


ARC STUD WELDING RECOMMENDED MINIMUM BASE METAL THICKNESS

STUD WELD BASE DIA. (in.)	STEEL		ALUMINUM	
	WITHOUT BACKUP		WITHOUT BACKUP	WITH BACKUP
	(in.)	(gage)	(in.)	(in.)
0.187	0.0359	20	0.125	0.125
0.250	0.0478	18	0.125	0.125
0.312	0.0598	16	0.187	0.125
0.375	0.0747	14	0.187	0.187
0.437	0.0897	13	0.250	0.187
0.500	0.1196	11	0.250	0.250
0.625	0.148	9		
0.750	0.187			
0.875	0.250			
1.000	0.375			

ARC STUD WELDING DC POWER SUPPLY REQUIREMENTS

POWER SUPPLY (NEMA RATED)	STUD WELD BASE DIAMETER IN INCHES
------------------------------	-----------------------------------

400 AMP UNIT
 600 AMP UNIT
 TWO-400 AMP UNITS IN PARALLEL
 TWO-600 AMP UNITS IN PARALLEL
 OR ONE MIDWEST FASTENERS UA-1800-PS
 ONE-2000 AMP UNIT
 OR ONE MIDWEST FASTENERS UA-2500-PS
 TWO-2000 AMP UNITS IN PARALLEL
 OR TWO MIDWEST FASTENERS UA-2500-PS'S
 IN PARALLEL

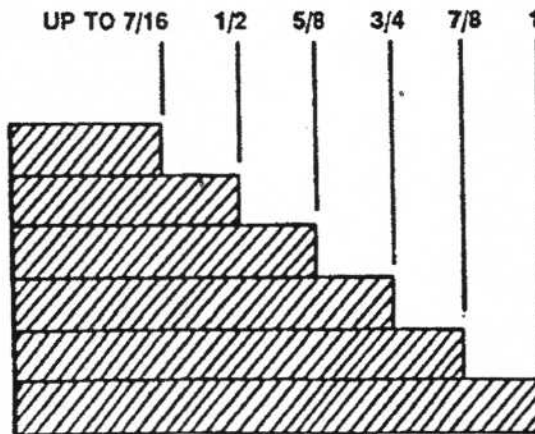

NEW-AGE
FASTENING SYSTEMS, INC.

Studwelding Equipment, Fasteners & Supplies
 Boiler Outage Specialists
 Jobsite Studwelding Division
 P.O. Box 5658, Deptford, NJ 08096
 Phone: (856) 218-8301
 Fax: (856) 218-8305
 Toll Free: (888) 889-3833
 steve@newagestudwelding.com

All information contained herein subject to change without notice.